

Strong hybridization-induced dispersive Kondo resonance in YbAl_2

M. Matsunami,^{1,2,*} T. Hajiri,¹ H. Miyazaki,^{1,†} M. Kosaka,³ and S. Kimura^{1,2}

¹*UVSOR Facility, Institute for Molecular Science, Okazaki 444-8585, Japan*

²*School of Physical Sciences, The Graduate University for Advanced Studies (SOKENDAI), Okazaki 444-8585, Japan*

³*Graduate School of Science and Engineering, Saitama University, Saitama 338-8570, Japan*

(Dated: October 30, 2012)

We report the electronic structure of a prototypical valence fluctuation system, YbAl_2 , using three-dimensional angle-resolved photoemission spectroscopy. The observed band dispersions and Fermi surfaces are well described in terms of band structure calculations based on local density approximation. Strong hybridization between the conduction and $4f$ bands was identified on the basis of the periodic Anderson model. Such findings suggest that the strong hybridization suppresses band renormalization and hence the electron correlation effect of the $\text{Yb}4f$ states does not work significantly. Even in this situation, the Kondo resonance peak can be defined and its dispersion is clearly observed, thus demonstrating the uniqueness of Yb-based compounds.

PACS numbers: 71.27.+a, 71.20.Eh, 75.30.Mb, 79.60.-i

Heavy-fermion or valence fluctuation systems are characterized by hybridization between the conduction (c) band and nearly localized f electrons with strong correlations, resulting in an enhanced effective mass of quasi-particles due to the band renormalization effect¹. Consequently, the Fermi surface (FS) topology is modified from that predicted in band structure calculations based on local density approximation (LDA). To estimate the impact on the FS topology of the band renormalization effect, a direct comparison of the experimental band structure as well as the FS with the calculations is necessary. Angle-resolved photoemission spectroscopy (ARPES), which can probe both band structure and FS topology, is the most suitable tool for this purpose.

The c - f hybridization-derived electronic structure including a Kondo resonance peak has been verified by ARPES studies^{2–13}. However, most of those studies have been performed on the basis of the surface Brillouin zone (BZ)^{2–6} or by using the $4d$ - $4f$ resonant process^{7–9}, in which k_z (momentum normal to surface) dependence of the electronic structure is neglected owing to its quasi-two dimensionality. In general, ARPES along the bulk BZ with well-defined k_z should be ideal for the three-dimensional (3D) electronic structure. Furthermore, ARPES data acquired at the high-symmetry point in the bulk BZ can be closely compared with the band structure calculations. In the case of Ce-based compounds, however, resonant photoemission is intrinsically required to directly probe the f -derived feature in the bonding band of the c - f hybridized bands because of the small f -electron occupation number ($n_f \sim 1$). On the other hand, in Yb-based compounds, the large occupation number ($n_f \sim 13$) enables us to probe the dispersions of not only the bonding band but also the anti-bonding band of the c - f hybridization without any resonant process, and hence the photon-energy ($h\nu$) tuning of k_z into the high-symmetry point is available. The Kondo resonance peak also exists on the occupied side, in contrast to Ce compounds and hence is accessible with ARPES. Therefore, as a starting point to establish the relationships among

the c - f hybridization, the Kondo resonance, and the band renormalization in heavy-fermion systems, the basic and simple Yb systems should be studied by means of 3D-ARPES.

Here, we focus on YbAl_2 as an ideal system to address the above issue. YbAl_2 is known as one of the prototypical valence fluctuation systems. The mass enhancement factor is particularly small among heavy-fermion systems known so far¹⁴. In a recent hard x-ray photoemission spectroscopy (HAXPES) study, the mean valence of Yb ions was estimated as $\sim +2.2$ below 300 K¹⁵. In addition, an extremely high Kondo temperature (T_K) exceeding 2000 K has been suggested by analysis of the Kondo resonance peak, as well as the magnetic susceptibility¹⁶ or the inelastic neutron scattering¹⁷.

In this Rapid Communication, we report the results of 3D-ARPES performed on YbAl_2 . The band structure and FSs obtained were comparable to those of the LDA calculation. The dispersions of the c - f hybridized bands and the Kondo resonance peaks near the Fermi level (E_F) were clearly observed and analyzed on the basis of a periodic Anderson model (PAM). The estimated mass enhancement factor and T_K are consistent with the thermodynamic measurements. These results suggest that the strong c - f hybridization suppresses the band renormalization and hence the electron correlation effect of $\text{Yb}4f$ states does not work significantly in YbAl_2 , even though rare-earth compounds are generally believed to have a strong correlation effect.

Single crystals of YbAl_2 were grown by the lithium flux method¹⁸. The 3D-ARPES experiment was carried out at the undulator beamline BL7U of UVSOR-II in the Institute for Molecular Science, with $h\nu = 16\sim 29$ eV and using a hemispherical electron analyzer (MBS A-1, MB Scientific)¹⁹. The total energy resolution and the measurement temperature were set to 20 meV and 12 K, respectively. The vacuum was maintained below 5×10^{-9} Pa during the experiment. The crystal orientation was determined by back-reflection Laue x-ray diffraction prior to the ARPES measure-

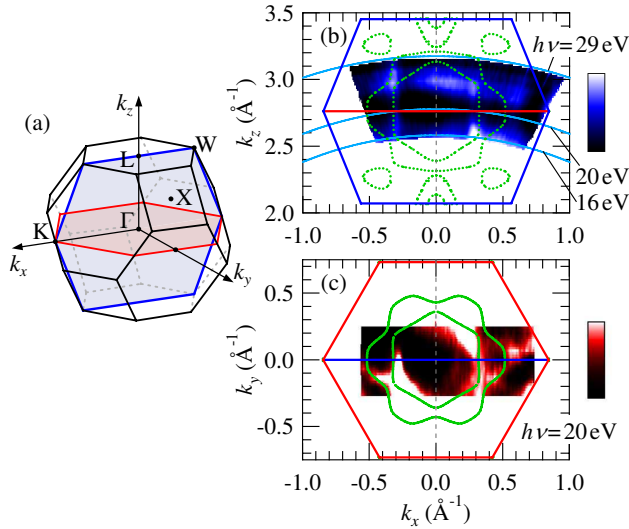


FIG. 1: (color online) (a) BZ of YbAl_2 , in which k_z corresponds to the (111) direction of the fcc BZ. (b) and (c) FS mapping in the k_x - k_z plane and k_x - k_y plane, respectively. The dotted and solid lines indicate the FSs obtained by the LDA calculation.

ments. Clean sample surfaces for ARPES measurements were obtained by cleaving *in situ* at 12K along the (111) plane. The LDA calculation was performed by the full-potential linearized-augmented-plane-wave plus local-orbital (LAPW+lo) method including spin-orbit coupling implemented in the WIEN2k code²⁰.

Figure 1 (a) shows the BZ of YbAl_2 , in which k_z corresponds to the (111) direction of the fcc BZ. The FS in the k_x - k_z plane is obtained from the $h\nu$ -dependent ARPES, as shown in Fig. 1 (b). The FS is obtained by a plot of the integrated intensity within $E_F \pm 50$ meV in the ARPES spectra. The inner potential is determined to be 13.7 eV from the symmetry of the FS-image contrast. Figure 1 (c) shows the “in-plane” FS in the k_x - k_y plane, measured at $h\nu = 20$ eV. The FS obtained from the LDA calculation is also plotted in Figs. 1 (b) and (c). Two FSs, both inner and outer, as predicted in the LDA calculation, are observed in both the k_x - k_z and k_x - k_y planes. In particular, the size of the inner FS matches well. A further comparison between the experimental results and calculations is given below on the basis of the band structure.

Figures 2 (a) and (b) show an intensity plot of the ARPES spectra taken along the Γ -K direction and their angle integrated spectrum, respectively, measured at $h\nu = 20$ eV. Both the widely dispersive c bands and the nearly dispersionless f bands are clearly visible in the ARPES image. Regarding the f bands, the main features at the binding energy (E_B) of 0.17 eV and 1.49 eV are attributed to the spin-orbit split components $4f_{7/2}$ and $4f_{5/2}$, respectively, in the bulk. The $4f_{7/2}$ peak was fitted by a Lorentzian multiplied by a Fermi-Dirac distribution (FDD) and an integral background, as shown

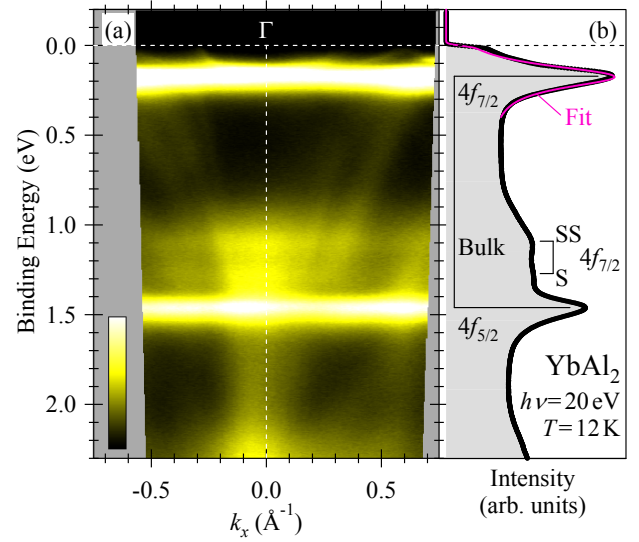


FIG. 2: (color online) (a) Intensity plot of the ARPES spectra of YbAl_2 taken along the Γ -K direction. (b) Angle-integrated spectrum obtained from (a). The $4f_{7/2}$ peak is fitted by a Lorentzian multiplied by an FDD and an integral background. “S” and “SS” denote the surface and subsurface states, respectively.

by the thin solid line in Fig. 2 (b). The peak position and width obtained were 0.171 eV and 0.155 eV, respectively, which are consistent with those in the HAXPES and soft x-ray photoemission spectra¹⁵. Additional fine structures can be seen at $E_B \sim 1.09$ eV and 1.25 eV, which might be derived from the subsurface and surface $4f_{7/2}$ states, respectively²¹. Such non-bulk components have little impact on the bulk $4f_{7/2}$ band, which is focused on in the following.

Figures 3 (a) and (b) show the series of ARPES spectra and the ARPES intensity plot, respectively, near E_F along the Γ -K direction. The band dispersions obtained from the LDA calculation are also plotted in Fig. 3 (b). The observed Yb $4f_{7/2}$ band around $E_B = 0.17$ eV shows good agreement of energy with the calculation, without any shift. The degree of coincidence is much greater than that of the other nearly divalent Yb system YbCu_2Ge_2 ¹³. To emphasize the c -band dispersions, each energy distribution curve (EDC) in the ARPES image is normalized to the angle-integrated spectrum in Fig. 2 (b). Alternatively, the same results can be achieved by normalization for each momentum distribution curve (MDC) area. The ARPES spectra and image obtained, shown in Figs. 3 (c) and (d), respectively, can be regarded as “effective off-resonance” ARPES spectra and image, representing hybridized-band dispersions. It should be noted that, unlike purely divalent systems²², the existence of these hybridized bands is responsible for the valence fluctuations in YbAl_2 . Their overall feature is well described in terms of the LDA calculation. In particular, among the anti-bonding bands located in the lower E_B region com-

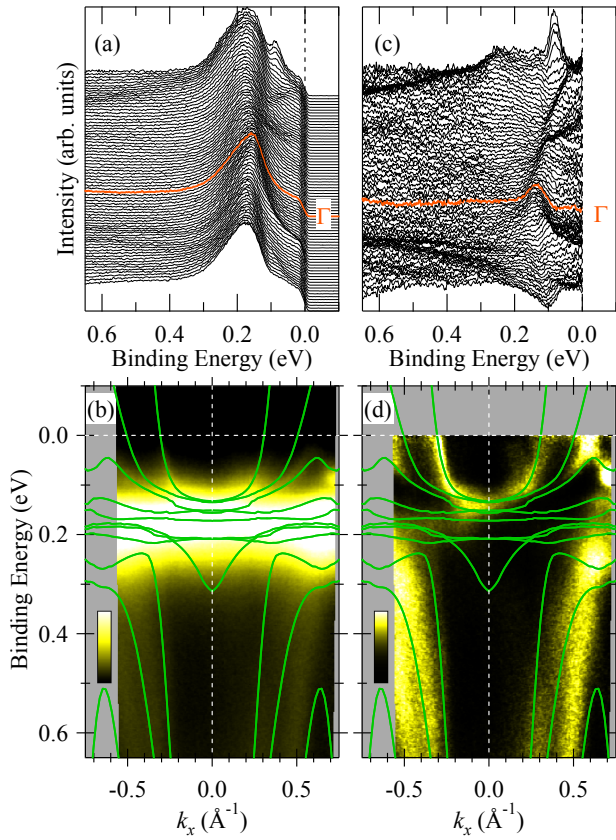


FIG. 3: (color online) (a) Series of ARPES spectra near E_F of YbAl_2 along the Γ -K direction. (b) ARPES intensity plots of (a) as a function of the wave vector. (c) and (d) The same data as in (a) and (b), respectively, normalized to the angle-integrated spectrum in Fig. 2 (b). The band dispersions obtained from the LDA calculation are overlapped in (b) and (d).

pared with the $4f_{7/2}$ band, the innermost band matches well. On the other hand, the experimental outer band has a slightly weaker dispersion. This band might be mixed with a more outer band, which does not cross E_F as shown in the LDA calculation. Similar slight deviation from the LDA calculation is recognized in the bonding bands shown in Fig. 3 (d).

In order to quantify the impact of the c - f hybridization effect apart from the LDA calculation, the observed band dispersions were analyzed in terms of PAM. In the non-interacting case with $U_{ff} = 0$, the band dispersion of PAM is given by the form of hybridized bands as

$$E_k^\pm = \frac{\varepsilon_k + E_{f,k} \pm \sqrt{(\varepsilon_k - E_{f,k})^2 + 4V_k^2}}{2}, \quad (1)$$

where ε_k , $E_{f,k}$, and V_k are the c -band, f -band, and hybridization energy, respectively¹. As a simplification to fit the experimental data using this formula, a parabolic electron band was assumed for ε_k and the k dependence of $E_{f,k}$ and V_k was neglected. The fitting result is shown

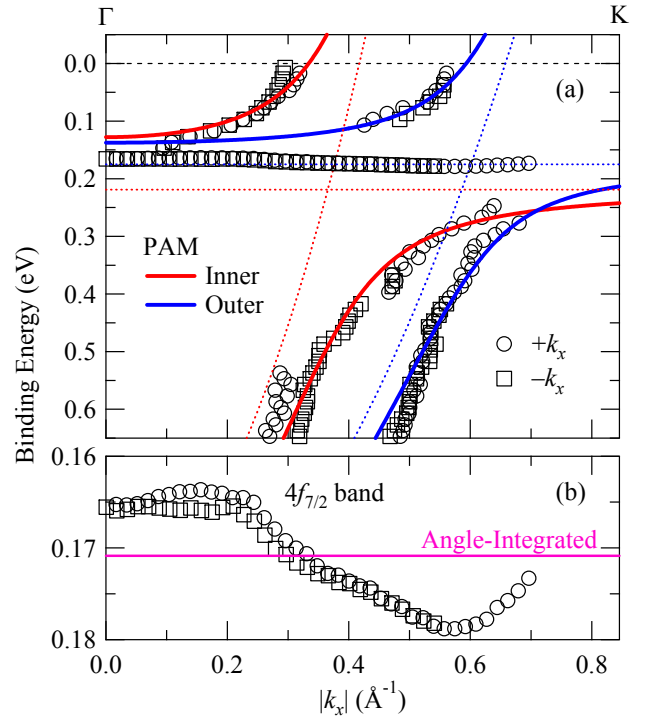


FIG. 4: (color online) (a) Analysis of band dispersions in YbAl_2 by c - f hybridized bands based on PAM. The experimental data points were obtained from a Lorentzian fitting of MDC or EDC. (b) Expansion of dispersion for the $4f_{7/2}$ -band; namely, the Kondo resonance peak. The angle-integrated data were obtained from the fitting in Fig. 2 (b).

in Fig. 4 (a), in which the experimental data points are obtained from a Lorentzian fitting of MDC or EDC and plotted as the absolute value of k_x . The band dispersions are well reproduced by this simple model with the parameters of $E_{f,\text{in}} = 0.219$ eV and $V_{\text{in}} = 0.272$ eV for the inner band and $E_{f,\text{out}} = 0.175$ eV and $V_{\text{out}} = 0.186$ eV for the outer band. From the value of E_f , T_K is evaluated as 2540 K and 2030 K for the inner and outer bands, respectively. In this case, the lower T_K is meaningful and consistent with that obtained by other experiments^{16,17}. The mass enhancement is simply related to the dispersion of E_k^+ and ε_k at each k_F by the relation

$$\frac{m^*}{m_b} = \frac{\partial^2 \varepsilon_k}{\partial k^2} / \frac{\partial^2 E_k^+}{\partial k^2}, \quad (2)$$

where m_b is the unhybridized band mass. The mass enhancement factor m^*/m_b is evaluated as 1.42 for the inner band and 2.79 for the outer band. Since the electronic specific heat coefficient γ of YbAl_2 has been reported as ~ 10 – 17 mJ/K²mol^{18,23}, and that of LuAl_2 as a reference is 5.7 mJ/K²mol²⁴, the ratio, $\gamma(\text{YbAl}_2)/\gamma(\text{LuAl}_2) = 1.8$ – 3 , is comparable to the mass enhancement obtained in our ARPES study. It is quite reasonable that the outer band, with its dispersion slightly deviated from the LDA calculation, has a heavier mass and a weaker hybridiza-

tion than the inner band.

The small mass enhancement observed in YbAl_2 can be described in terms of a c - f hybridization effect. However, the renormalization effect due to the electron correlation U_{ff} cannot contribute significantly. Even if the parameters obtained from this analysis include a renormalization effect in some manner such as $\tilde{E}_f$ and $\tilde{V}$, the impact would be very small, as expected from the degree of mass enhancement. More importantly, the coincidence of the $4f_{7/2}$ band position with that in the LDA calculation strongly suggests an extremely small renormalization. It is also consistent with the weak renormalization factor suggested in the optical conductivity of YbAl_2 ²⁵. Such a suppressed renormalization should be caused by the strong c - f hybridization. Therefore, PAM analysis under the condition of $U_{ff} = 0$ can be useful in the case of YbAl_2 .

Finally, we consider the $4f_{7/2}$ peak around $E_B = 0.17$ eV in terms of a Kondo resonance peak, not merely a shallow core level. As shown in Fig. 4 (b), this peak shows a small but clear dispersion between the Γ and K points. Such behavior is consistent with the theoretical predictions on the basis of PAM²⁶. This finding therefore provides evidence for the dispersion of the Kondo resonance peak in the coherent Kondo ground state. In spite of the extremely small renormalization, the identification of a Kondo effect, which represents a typical many-body phenomenon¹, may seem to be unreasonable. In Yb-based compounds, however, the Kondo state can exist over a broad range of Yb valence between +2 and +3, based on the fact that the spin-orbit splitting of Yb $4f$ electrons is generally larger than the $4f$ bandwidth²⁷. This description contrasts with the Ce case, in which

the Kondo state can exist only near +3 and the Ce $4f$ spin-orbit splitting is smaller than the $4f$ bandwidth. In the case of YbAl_2 , the Yb valence is nearly divalent +2.2 as a consequence of the strong c - f hybridization¹⁵. With decreasing hybridization strength toward Yb^{3+} , the Kondo resonance peak will move closer to E_F and become sharper. Such an evolution of Kondo resonance may bring about the drastically modified FS topology and the highly renormalized band structure compared with the LDA calculation. In contrast, at the Yb^{2+} limit, the Kondo resonance peak turns into the shallow core level of the $4f_{7/2}$ states and does not contribute to the FS²². As a result, in YbAl_2 , the coherent Kondo state coexists sufficiently well with the nearly unrenormalized band structure to match with the LDA calculation. It can, therefore, be concluded that YbAl_2 is a well-balanced system characterized by unrenormalized Kondo resonance. This demonstration of the uniqueness of Yb-based compounds provides important insights into heavy-fermion physics.

In conclusion, we have performed 3D-ARPES of a prototypical valence fluctuation system YbAl_2 . The band dispersions obtained around the Γ point, particularly the energy position of the Yb $4f_{7/2}$ bands, are well described by the LDA calculation without any modification. This may indicate that the electron correlation of Yb $4f$ states does not work significantly. A strongly c - f hybridized nature and dispersive Kondo resonance peak were identified on the basis of PAM. These results suggest a well-balanced coexistence between the coherent Kondo state and the nearly unrenormalized band structure in YbAl_2 .

We would like to thank T. Ito for fruitful discussions. This work was performed by the Use-of-UVSOR Facility Program of the Institute for Molecular Science (2011).

* Electronic address: matunami@ims.ac.jp

† Present address: Faculty of Engineering, Nagoya Institute of Technology, Nagoya 466-8555, Japan

¹ A. C. Hewson, *The Kondo Problem to Heavy Fermions* (Cambridge University Press, Cambridge, 1993).

² A. J. Arko, J. J. Joyce, D. P. Moore, J. L. Sarrao, L. Morales, T. Durakiewicz, Z. Fisk, D. D. Koelling, and C. G. Olson, *J. Electron Spectrosc. Relat. Phenom.* **117**, 323 (2001).

³ S. Danzenbächer, Yu. Kucherenko, C. Laubschat, D. V. Vyalikh, Z. Hossain, C. Geibel, X. J. Zhou, W. L. Yang, N. Mannella, Z. Hussain, Z.-X. Shen, and S. L. Molodtsov, *Phys. Rev. Lett.* **96**, 106402 (2006).

⁴ G. A. Wigger, F. Baumberger, Z.-X. Shen, Z. P. Yin, W. E. Pickett, S. Maquilon, and Z. Fisk, *Phys. Rev. B* **76**, 035106 (2007).

⁵ D. V. Vyalikh, S. Danzenbächer, Yu. Kucherenko, K. Kummer, C. Krellner, C. Geibel, M. G. Holder, T. K. Kim, C. Laubschat, M. Shi, L. Patthey, R. Follath, and S. L. Molodtsov, *Phys. Rev. Lett.* **105**, 237601 (2010).

⁶ S.-K. Mo, W. S. Lee, F. Schmitt, Y. L. Chen, D. H. Lu, C. Capan, D. J. Kim, Z. Fisk, C.-Q. Zhang, Z. Hussain, and Z.-X. Shen, *Phys. Rev. B* **85**, 241103(R) (2012).

⁷ H. J. Im, T. Ito, H.-D. Kim, S. Kimura, K. E. Lee, J. B. Hong, Y. S. Kwon, A. Yasui, and H. Yamagami, *Phys. Rev. Lett.* **100**, 176402 (2008).

⁸ A. Koitzsch, S. V. Borisenko, D. Inosov, J. Geck, V. B. Zabolotnyy, H. Shiozawa, M. Knupfer, J. Fink, B. Büchner, E. D. Bauer, J. L. Sarrao, and R. Follath, *Phys. Rev. B* **77**, 155128 (2008).

⁹ M. Klein, A. Nuber, H. Schwab, C. Albers, N. Tobita, M. Higashiguchi, J. Jiang, S. Fukuda, K. Tanaka, K. Shimada, M. Mulazzi, F. F. Assaad, and F. Reinert, *Phys. Rev. Lett.* **106**, 186407 (2011).

¹⁰ J. D. Denlinger, G.-H. Gweon, J. W. Allen, C. G. Olson, M. B. Maple, J. L. Sarrao, P. E. Armstrong, Z. Fisk, and H. Yamagami, *J. Electron Spectrosc. Relat. Phenom.* **117**, 347 (2001).

¹¹ M. Yano, A. Sekiyama, H. Fujiwara, T. Saita, S. Imada, T. Muro, Y. Ōnuki, and S. Suga, *Phys. Rev. Lett.* **98**, 036405 (2007).

¹² T. Okane, T. Ohkouchi, Y. Takeda, S.-i. Fujimori, A. Yasui, Y. Saitoh, H. Yamagami, A. Fujimori, Y. Matsumoto, M. Sugi, N. Kimura, T. Komatsubara, and H. Aoki, *Phys. Rev. Lett.* **102**, 216401 (2009).

¹³ A. Yasui, S.-I. Fujimori, I. Kawasaki, T. Okane, Y. Takeda,

- Y. Saitoh, H. Yamagami, A. Sekiyama, R. Settai, T. D. Matsuda, Y. Haga, and Y. Ōnuki, Phys. Rev. B **84**, 195121 (2011).
- ¹⁴ N. Tsujii, H. Kontani, and K. Yoshimura, Phys. Rev. Lett. **94**, 057201 (2005).
- ¹⁵ M. Matsunami, A. Chainani, M. Taguchi, R. Eguchi, Y. Takata, M. Oura, M. Yabashi, K. Tamasaku, Y. Nishino, T. Ishikawa, M. Kosaka, and S. Shin, J. Phys. Soc. Jpn. **81**, 073702 (2012).
- ¹⁶ Generally, the Kondo temperature T_K is defined as $3T_{\max}$, where $T_{\max}$ is the temperature showing a broad maximum in the magnetic susceptibility. For YbAl_2 , $T_{\max}$ is estimated as 800–850 K as reported in J. C. P. Klaasse, J. W. E. Sterkenburg, A. H. M. Bleyendaal, and F. R. de Boer, Solid State Commun. **12**, 561 (1973); and in E. E. Havinga, K. H. J. Buschow, and H. J. van Daal, *ibid.* **13**, 621 (1973).
- ¹⁷ A. P. Murani, A. D. Taylor, R. Osborn, and Z. A. Bowden, Philos. Mag. B **65** 1333 (1992).
- ¹⁸ H. Nowatari, Y. Saiga, Y. Kato, K. Iwata, S. Katano, T. Fujiwara, Y. Uwatoko, and M. Kosaka, J. Phys. Soc. Jpn. **76**, 80 (2007).
- ¹⁹ S. Kimura, T. Ito, M. Sakai, E. Nakamura, N. Kondo, T. Horigome, K. Hayashi, M. Hosaka, M. Katoh, T. Goto, T. Ejima, and K. Soda, Rev. Sci. Instrum. **81**, 053104 (2010).
- ²⁰ P. Blaha, K. Schwarz, P. Sorantin and S. B. Trickey, Comput. Phys. Commun. **59**, 399 (1990).
- ²¹ G. Kaindl, B. Reihl, D. E. Eastman, R. A. Pollak, N. Mårtensson, B. Barbara, T. Penney, and T. S. Plaskett, Solid State Commun. **41**, 157 (1982).
- ²² M. Matsunami, A. Chainani, M. Taguchi, R. Eguchi, Y. Ishida, Y. Takata, H. Okamura, T. Nanba, M. Yabashi, K. Tamasaku, Y. Nishino, T. Ishikawa, Y. Senba, H. Ohashi, N. Tsujii, A. Ochiai, and S. Shin, Phys. Rev. B **78**, 195118 (2008).
- ²³ Z. Fisk and M. B. Maple, J. Alloys Compounds **183**, 303 (1992).
- ²⁴ R. E. Hunsberg and K. A. Gschneidner, Jr., J. Phys. Chem. Solids **33**, 401 (1972).
- ²⁵ S. I. Kimura, Phys. Rev. B **80**, 073103 (2009).
- ²⁶ A. N. Tahvildar-Zadeh, M. Jarrell, and J. K. Freericks, Phys. Rev. Lett. **80**, 5168 (1998).
- ²⁷ J. Flouquet and H. Harima, arXiv:0910.3110.